

Electrical transport properties of bulk tetragonal CuMnAs

J. Volný,¹ D. Wagenknecht,¹ J. Železný,² P. Harcuba,³ E. Duverger–Nedellec,¹
R.H. Colman,¹ J. Kudrnovský,⁴ I. Turek,¹ K. Uhlířová,¹ and K. Vybírný²

¹Charles University, Faculty of Mathematics and Physics,

Department of Condensed Matter Physics, Ke Karlovu 5, Praha 2, CZ–12116, Czech Republic

²Institute of Physics, Academy of Science of the Czech Rep., Cukrovarnická 10, Praha 6, CZ–16253

³Charles University, Faculty of Math. and Physics, Dep. of Material Physics, Ke Karlovu 5, Praha 2, CZ–12116

⁴Institute of Physics, Academy of Science of the Czech Rep., Na Slovance 2, Praha 8, CZ–18221

(Dated: Jan13, 2020)

Temperature-dependent resistivity $\rho(T)$ and magnetoresistance are measured in bulk tetragonal phase of antiferromagnetic CuMnAs and the latter is found to be anisotropic both due to structure and magnetic order. We compare these findings to model calculations with chemical disorder and finite-temperature phenomena included. The finite-temperature *ab initio* calculations are based on the alloy analogy model implemented within the coherent potential approximation and the results are in fair agreement with experimental data. Regarding the anisotropic magnetoresistance (AMR) which reaches a modest magnitude of 0.12%, we phenomenologically employ the Stoner-Wohlfarth model to identify temperature-dependent magnetic anisotropy of our samples and conclude that the field-dependence of AMR is more similar to that of antiferromagnets than ferromagnets, suggesting that the origin of AMR is *not* related to isolated Mn magnetic moments.

The emergent field of antiferromagnetic (AFM) spintronics¹ has brought one particular AFM metal to prominence: CuMnAs. Apart from electrical switching² and domain wall manipulation³ the main focus in exploring its response to electric field has so far been on the optical range (ellipsometry and photoemission spectroscopy used to validate band structure calculations⁴) and also on the staggered spin polarisation induced by electric field.⁵ The latter led to the discovery of an efficient means to manipulate⁶ magnetic moments in an AFM and this, in turn, allowed the construction of memory prototypes operating at room temperature⁷ where information is stored in the direction of magnetic moments. As a method for read-out, anisotropic magnetoresistance (AMR) is used and the primary aim of this work is to explore this very phenomenon in CuMnAs. Contrary to previous recent studies of CuMnAs which entailed epitaxially grown thin layers,⁸ we now focus on bulk material.

In the bulk form, CuMnAs was originally reported to have orthorhombic structure⁹ while thin films grown on GaP or GaAs substrates¹⁰ grow in a tetragonal phase. Recent studies of off-stoichiometric $\text{Cu}_{1+x}\text{Mn}_{1-x}\text{As}$ compounds¹¹ have shown^{12,13} that their crystal structure is rather sensitive to the composition. While the stoichiometric CuMnAs compounds crystallise in an orthorhombic structure (Pnma), few percent of copper excess at the expense of Mn turns the structure to a tetragonal one (P4/nmm). In the tetragonal phase, the Néel temperature reaches 507 K for $\text{Cu}_{1.02}\text{Mn}_{0.99}\text{As}$ and decreases with decreasing Mn content rather moderately; samples with more off-stoichiometric composition have lower Néel temperatures, for example ≈ 300 K for¹³ $x = 0.4$. Our focus, however, will be on the nearly-stoichiometric tetragonal systems.

The following section describes the fabrication of samples for electrical transport measurements from a single-crystalline grain and acquired experimental data. Mod-

elling and interpretative approaches are introduced in Sec. II and sections III and IV are devoted to models of zero-field transport and AMR, respectively. The two appendices focus on magnetic anisotropy of CuMnAs and its modelling and certain specialised aspects of micro-

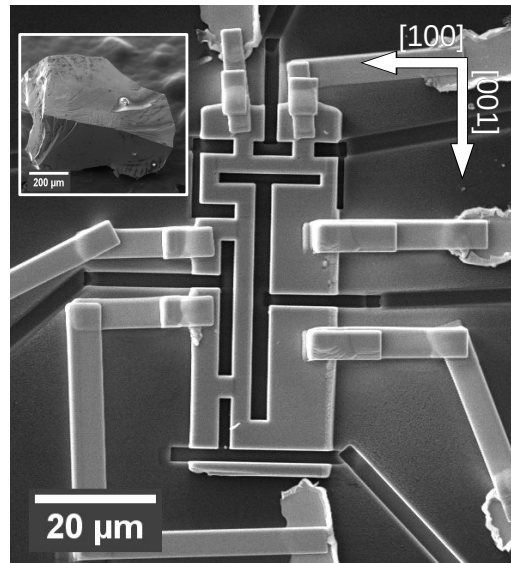


FIG. 1. Scanning electron microscope (SEM) image of the device and the single-crystalline grain from which it was fabricated.

scopic transport calculations.

I. EXPERIMENTAL

A. Growth and preparation

A sample of tetragonal CuMnAs was prepared by reaction of high purity copper, manganese and arsenic as previously reported.¹³ Tetragonal P4/nmm structure was confirmed by powder x-ray diffraction at room temperature on Bruker D8 Advance diffractometer.¹³ Composition analysis performed by energy-dispersive x-ray detector (EDX) suggests a slight prevalence of copper, the stoichiometry being 1.02(1):0.99(2):0.99(2) for Cu:Mn:As; Néel temperature (T_N) is 507 K. From thus obtained polycrystal, a single-crystal grain was cleaved, oriented using x-ray diffraction and its orientation was further refined on an SEM stub holder using electron backscatter diffraction (EBSD).

For transport measurements, we adopted the sample fabrication introduced by Moll et al.^{14–16} A rectangular lamella extending in the ac -directions of dimensions $60 \times 20 \times 3 \mu\text{m}^3$ was isolated out of a single-crystal grain using 30 kV Ga²⁺ Focused Ion Beam (FIB) Tescan Lyra XMH and transported to sapphire chip with contact pads (5 nm Cr + 150 nm Au) prepared by photolithography. The lamella was microstructured into a shape presented in Fig. 1 and it was conductively bonded to the contact pads using FIB assisted chemical vapor deposition of Pt. Typical resistance of each contact prepared by this method was around 50 Ω . To improve the contact resistance, we further sputtered the sample with a 100 nm Au layer and removed the excess gold from the top of our sample and in between the contacts using the FIB. This resulted in an order of magnitude lower resistance of 5 Ω per contact.

This method allows us to precisely control the orientation of the sample, which is essential due to highly anisotropic behaviour of CuMnAs which we demonstrate in the following. Furthermore, structuring the sample into a long thin bar allows us to obtain a high signal-to-noise ratio without using high current and thus avoiding self heating at low temperatures.

Resistivity measurement in a temperature range from 2 to 400 K was carried out using a Quantum Design Physical Property Measurement System with a Horizontal Rotator option. Typical currents were of the order of 100 μA which translates into current densities ranging from 0.5 to $2 \times 10^7 \text{ Am}^{-2}$ (small compared to what is used in CuMnAs-based memory devices as writing pulses²). The error in calculating geometrical factor of the bulk device presented here is about 15 %. This translates into a substantial part of error in determining the bulk resistivity.

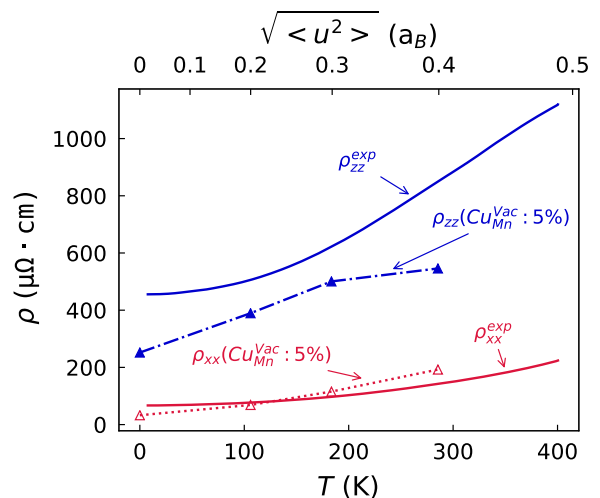


FIG. 2. Resistivity of bulk CuMnAs measured along a - (in-plane, ρ_{xx}) and c -axes (out-of-plane, ρ_{zz}) shown by solid lines. To demonstrate a typical level of agreement with model calculations, resistivity assuming scattering on static impurities ($\text{Cu}_{\text{Mn}}^{\text{vac}}$ as explained¹⁷ later in Sec. III) and phonons is also shown.

B. Transport measurements

Transport properties of tetragonal CuMnAs have previously been explored only in thin films.⁸ Since all epitaxial growth processes reported so far occur in the (001) direction, only in-plane resistivity (ρ_{xx} or a -axis direction) can be found in literature. Contrary to the thin films, our bulk devices allow both ρ_{xx} and the out-of-plane component ρ_{zz} to be measured. In-plane data in Fig. 2 are similar to previously published results⁸ and we take notice of the large structural anisotropy, i.e. resistivity along the c -axis being almost an order of magnitude larger (at low temperatures, the ratio to in-plane resistivity is 6.8 ± 0.8 and it slightly decreases at higher temperature). Given the layered structure of CuMnAs, this fact is perhaps not very surprising. Low-temperature $\rho_{xx} = 67 \pm 10 \mu\Omega\text{-cm}$ is somewhat lower (about 20%) than for thin layers of Ref. 8. This may be due to slightly different composition of the compared materials or sample quality; the residual resistivity ratios (RRRs) of bulk and thin films samples are 2.2 and 1.8, respectively, and more recent samples¹⁰ reach an even higher RRR of 3. An example of model calculations in Fig. 2 is further discussed below (see Sec. III): for now, the data points (triangles) should only demonstrate the typical level of agreement with one specific sort of impurities consistent with the known chemical composition of the studied samples. We stress that a significantly better level of agreement is achievable but only at the cost of less realistic model parameters (such as impurity concentration).

When a magnetic field is switched on, we find a very different response for in-plane and out-of-plane directions: the former shows a negative magnetoresistance

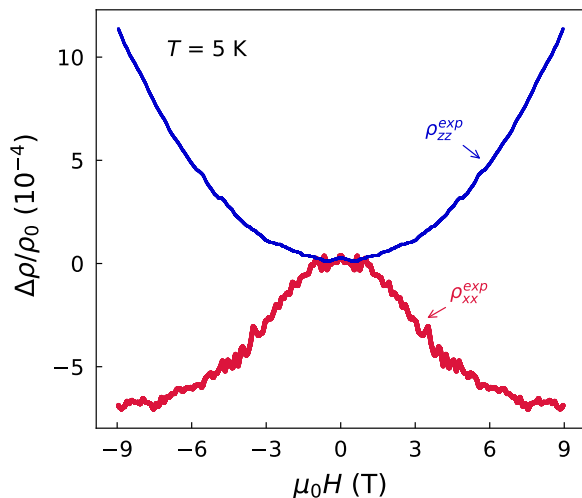


FIG. 3. Low temperature magnetoresistance normalised to zero field value R_0 (which is different for the two directions of current).

— common in magnetic materials when an applied field suppresses spin fluctuations — but $\rho_{zz}(B)$ increases, see Fig. 3. In both cases, the magnetic field is perpendicular to the current direction, i.e. along [010]. Apart from the AMR effect, the negative magnetoresistance could be related to some kind of magnetic moment response to the applied magnetic field (it is prominent at lower B) while the usual positive magnetoresistance in metals dominates at larger magnetic fields. For current along the c -axis, the manipulation of magnetic moments is of no effect (they always remain perpendicular to the current direction) and only the positive magnetoresistance remains.

Focusing on in-plane magnetotransport, we also find a clear anisotropy (i.e. ρ_{xx} different from ρ_{yy} when $\vec{B} \parallel \hat{x}$).¹⁹ Here, it should be noted that large magnetic anisotropies force the Néel vector into the ab -plane (see Appendix A) and conceivably, there remain weak in-plane anisotropies which allow for the magnetic moments to be moved within the plane easily. Angular sweeps shown in Fig. 4 suggest both the presence of AMR and temperature-dependent magnetic anisotropies which we discuss in Sec. IV. We observe a gradual increase of the AMR amplitude up to ≈ 6 T and above this magnetic field, the AMR signal does not change (measured up to 9 T, not shown). Low temperature ($T = 4$ K) and close-to-Néel-temperature ($T = 400$ K $< T_N$) measurements show clearly different distortion of the $\Delta\rho_{xx}(\psi) \propto \cos 2\psi$ signal, see also Eq. (3). Such cosine-squared form would be typical of polycrystalline samples¹⁸ if magnetocrystalline anisotropy were negligible (ψ is the angle between \vec{B} and the current direction).

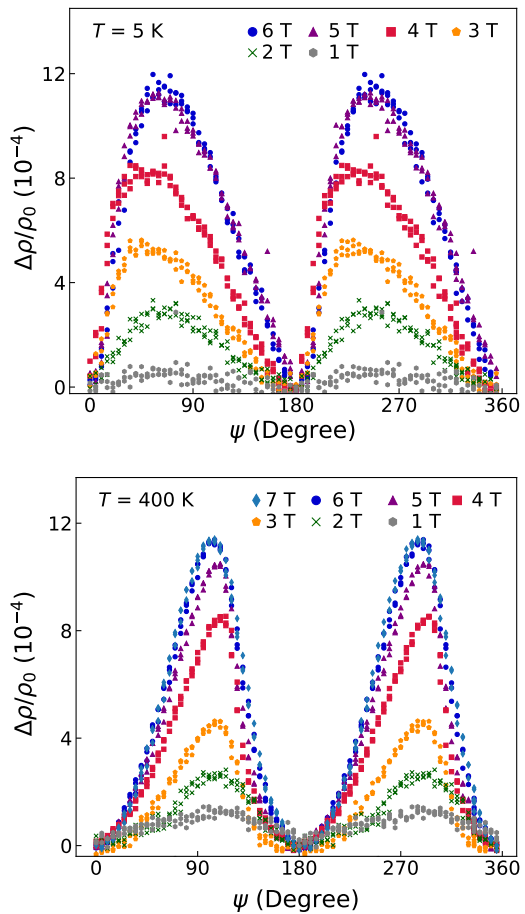


FIG. 4. Angular sweeps (magnetic field rotated in the plane) of ρ_{xx} showing AMR which deviates from the $\Delta\rho_{xx} \propto \cos^2 \psi$ dependence. Within the sweep, ρ_0 is the minimum value of resistivity. *Top*: low temperature, *bottom*: high temperature.

II. INTRODUCTION TO MODELLING

We employ two approaches to interpret our measured data: a microscopic model of electric transport where the direction of magnetic moments present in the system is assumed to be known; and a phenomenological one based on a Stoner-Wohlfarth model where the coupling between external magnetic field and magnetic order of CuMnAs samples is investigated. The latter approach allows to partially overcome our lack of knowledge about the precise nature of potential magnetic impurities. It serves the purpose of interpreting angular sweeps in Fig. 4 where the externally controlled parameter is ψ rather than directly the magnetic moments.

Our microscopic modelling is based on the tight-binding linear muffin-tin orbital (TB-LMTO) method with the atomic sphere approximation and the multi-component coherent potential approximation (CPA)²⁰. Calculations employ the Vosko-Wilk-Nusair exchange-correlation potential²¹ and Hubbard U was used in the fully relativistic LSDA+ U scheme for d -orbitals of Mn,

similarly to Refs. 22 (TB-LMTO) and 4 (LAPW). The value $U = 0.1$ Ry quoted in Tab. I was found consistent with optical and photoemission spectra in the latter reference. The scalar-relativistic methods (see Tab. V in Appendix B) are used only for a comparison with previous results.^{23,24} Band structures yielded by different approaches (including *GW*) can be found in Ref. 22.

Electrical transport properties are studied in a framework of the linear response theory and the Kubo-Bastin formula,²⁵ the velocity operators describe inter-site hoppings²⁶ and we take into account CPA-vertex corrections.²⁷ Longitudinal conductivities are given only by the Fermi-surface term; therefore, the Fermi-sea contribution²⁸ is omitted. Finite-temperature atomic displacements (phonons) are treated by alloy analogy model (AAM)^{29–32}; this model has recently been incorporated into the TB-LMTO-CPA technique.

For the inclusion of phonons, an extended *spdf*-basis is needed because of transformations of the LMTO potential functions.^{33,34} To compare novel results with literature,^{23,24} a few *spd*-calculations are shown in Appendix (Tab. V). Fluctuations of magnetic moments at nonzero temperatures are included by the tilting model³⁵ which was shown to describe low-temperature electrical transport of CuMnAs well.²² Tilting of magnetic moments from their equilibrium direction could be also included within the AAM³² as well as our TB-LMTO AAM²², but it is beyond the scope of this study. Zero-temperature calculations that involve magnetic impurities (such as Mn atom substituting Cu or As) are also based on the DLM approach. With this machinery at hand, temperature-dependent resistivity can successfully be modelled, provided we specify the source of scattering at $T = 0$ (otherwise, $\rho \rightarrow 0$ at low temperatures).

Defect	Formation energy [eV] ²⁴	Resistivity [$\mu\Omega\text{cm}$]			
		$U = 0.00$ Ry		$U = 0.10$ Ry	
		ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}
Vac _{Mn}	-0.16	31	184	20	181
Vac _{Cu}	-0.14	16	79	11	92
Mn _{Cu}	-0.03	112	263	150	915
Cu _{Mn}	0.34	23	131	8	57
Cu _{As}	1.15	121	481	163	1299
As _{Cu}	1.73	114	359	123	694
As _{Mn}	1.79	141	476	161	617
Mn _{As}	1.92	147	423	186	1784
Vac _{As}	2.18	210	306	284	1556
Cu \leftrightarrow Mn	-	120	393	142	882

TABLE I. Comparison of various impurity types in tetragonal CuMnAs (e.g. Vac_{Cu} or Mn_{Cu} indicate a copper vacancy and Mn atom substituting Cu, respectively). Calculated formation energy suggests that impurities involving arsenic are unlikely. Fully relativistic *spdf* calculations of resistivity are given for 5% of the respective impurity.

III. AB INITIO TRANSPORT AT ZERO FIELD

We first focus on residual resistivity. Experimentally, we know that stoichiometry of our CuMnAs samples is 1:1:1 within a few per cent margin and that puts a limit of maximum impurity concentration. Tab. I gives an overview of calculated resistivities for various types of impurities (5% of the respective impurity). It should be pointed out that fundamentally different sources of scattering than those listed in Tab. I may occur (even at zero temperature), e.g. structural defects such as 'fault lines' have recently¹⁰ been identified in epitaxial layers.

With this provision, the following conclusions can be drawn regarding resistivities in the absence of external magnetic field. (i) In a very broad picture, all of the listed values of resistivities are plausible; note that exact concentration of impurities is not known for our samples so even large values of ρ seen in Tab. I could be compatible with experimental data in Fig. 2 supposing the given type of impurity occurs at a low concentration. (ii) All listed cases involve a clear structural anisotropy $\rho_{zz}/\rho_{xx} > 1$. These two basic observations do not principally exclude any of the options in the table, however, (iii) defects involving arsenic, both as a dopant or as a site, seem unlikely given prohibitive formation energies.²⁴ (iv) Among the five remaining options, those compatible with Cu-rich stoichiometry show resistivity somewhat low compared to experimental data. (v) At this point (i.e. based on calculations in Tab. I), the most likely scenario, disregarding additional sources of scattering,¹⁰ would thus entail a combination of at least two types of impurities: for example Cu substituting Mn (Cu_{Mn}) and a Cu/Mn swap (Cu \leftrightarrow Mn), both at concentrations of few per cent.

Next, we consider the temperature dependence of resistivity and here, the primary source of scattering are the phonons. As a note of caution, we remark that calculated results are plotted as a function of $\sqrt{\langle u^2 \rangle}$ and conversion³⁶ into T requires the knowledge of Debye temperature T_D . (We use the value from orthorhombic phase, see Ref. 22 for explanation.) Calculations with 5% of Cu_{Mn} and $U = 0$ in Fig. 5 show a reasonable trend but overall values (in particular, of ρ_{zz}) are too low. Combination with other types of impurities such as¹⁷ Cu_{Mn}^{vac} offers a partial remedy (see model data in Fig. 2) but since concentration-dependence of resistivity is not always linear (see Appendix B and Fig. 9), construction of a quantitative model is difficult. We note that decreasing resistivity for high magnitudes of atomic displacements (see Fig. 5) is probably caused by an increase of DOS at the Fermi level, similarly the effect of magnons and phonons.²² The same effect may be responsible for nonmonotonic dependence of resistivity on concentration of Cu_{Mn}^{vac}: both observations clearly contradict the Matthiessen rule and are further discussed in Appendix B.

With temperature-dependent resistivity, phonons are not the sole source of scattering to be considered; rather, combined effect of impurities, phonons, and magnons

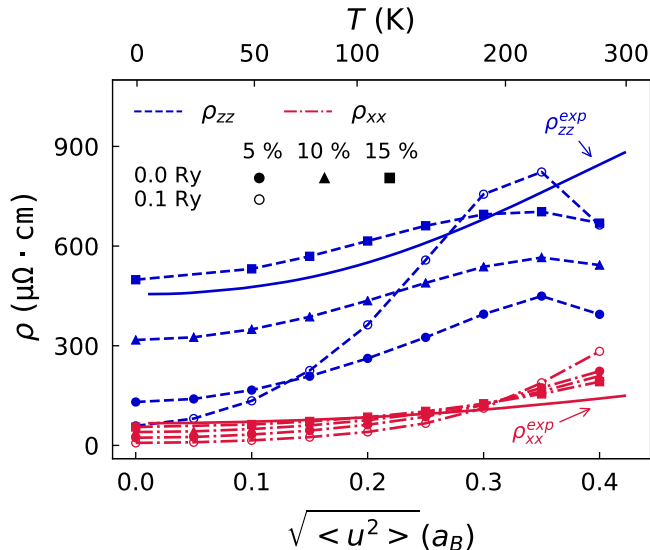


FIG. 5. Resistivity of CuMnAs calculated microscopically assuming finite-temperature atomic displacements $\sqrt{\langle u^2 \rangle}$ (modelling phonons) and Cu_{Mn} impurities (modelling the source of residual resistance at low temperature) at various concentrations.

should be taken into account. Above, we have shown a deviation of the resistivity from Matthiessen's rule for impurities and phonons; in Ref. 22, the same was reported for phonons and magnons. In that reference, we numerically justified a collinear uncompensated disordered local moment (uDLM) model of spin fluctuations and we demonstrated, that the tilting model of the magnetic disorder agrees well with experimental data up to room temperature. We now adopt the second approach and illustrate the combined effect of phonons and magnons and static Cu_{Mn} impurities. A similar model was discussed in Ref. 37 (relativistic effects in this context can also be considered³⁸). A decrease of mean local magnetic moment of Mn atoms was mapped on Monte-Carlo simulations²⁴ to obtain the temperature dependence of the spin fluctuations.^{22,36} Data presented in Tab. II show that even for lower concentration of Cu_{Mn} , the combined effect of phonon and magnon scattering close to the room temperature leads to ρ_{xx} clearly exceeding the experimental values while ρ_{zz} remains underestimated.

The underestimated values of structural anisotropy ρ_{zz}/ρ_{xx} seem to be a general feature of our calculations. Previous calculations were obtained without U (except for one dataset in Fig. 5 which we wish to discuss now); however, the electronic structure has not yet been reliably determined and the LSDA+ U agrees the best with GW calculations²² when $U = 0.20$ Ry. We emphasize, that the band structure pertains to CuMnAs without any disorder, while the transport is studied in disordered samples. Therefore, we consider the band structure to be of lesser importance for explaining the electrical transport than the DOS. The temperature-dependent resis-

TABLE II. Resistivity (in $\mu\Omega$ cm) due to a combined effect of static impurities (the sole source of scattering at $T = 0$), phonons and magnons (tilting model).

T [K]	Effects	Cu_{Mn} : 5 %		Cu_{Mn} : 10 %	
		ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}
0	-	23	131	41	319
65	Ph.	39	190	55	371
	Mag.	40	215	55	428
	P.+M.	59	269	72	474
230	Ph.	172	450	161	566
	Mag.	115	474	110	724
	P.+M.	257	345	263	450

tivity for $U = 0.20$ Ry increases about twice faster than both measured data and $U = 0.00$ Ry calculations; see Fig. 5 for Cu_{Mn} . We have investigated also the role of U on other impurities and finite-temperature disorder (not shown here) and, in general, nonzero Hubbard parameter makes both increase and decrease of the resistivity more significant (compared to U vanishing). This can be attributed to decreasing DOS²² around E_F for increasing U and, therefore, a larger sensitivity of electrical transport on small changes (caused by impurities or finite-temperature disorder).

IV. AMR MODELLING

Experimental data (angular sweeps in Fig. 4) show a pronounced AMR with two-fold symmetry reaching $\Delta\rho_{xx}/\rho_0 \sim 10^{-3}$ at saturation (here, ρ_0 is the planar average of resistivity). Theoretical data, see Tab. III, suggest that this magnitude of AMR is compatible with basically any type of disorder considered so far. Larger theoretical values (compared to the measured ones), however, indicate that it is not the whole system that responds to the applied magnetic field \vec{B} . In case of Cu/Mn swaps, the difference is extreme so either this defect is not very common in our samples or it is largely insensitive to \vec{B} .

Without specifying what in reality responds to magnetic field (bulk of the system, decoupled magnetic moments etc.), we can phenomenologically use the Stoner-Wohlfarth (SW) model to analyse data in Fig. 4. It can easily be adapted to study either ferromagnets (as originally conceived³⁹) or antiferromagnets⁴⁰. In the latter case, energy (per volume) divided by sublattice magnetisation M reads

$$\frac{E}{MV} = B_e \vec{m}_1 \cdot \vec{m}_2 - B \vec{b} \cdot (\vec{m}_1 + \vec{m}_2) + B_a [(\vec{m}_1 \cdot \hat{a})^2 + (\vec{m}_2 \cdot \hat{a})^2]. \quad (1)$$

while for ferromagnets, the exchange term (described by field B_e) between sublattices $\vec{m}_{1,2}$ is not present

$$\frac{E}{MV} = -B \vec{b} \cdot \vec{m} + B_a (\vec{m} \cdot \hat{a})^2. \quad (2)$$

Defect	Fully rel., <i>spd</i>		Fully rel., <i>spdf</i>	
	$U = 0$	$U = 0.10 \text{ Ry}$	$U = 0$	$U = 0.10 \text{ Ry}$
Vac _{Mn}	$6.09 \cdot 10^{-3}$	$1.16 \cdot 10^{-2}$	$-2.08 \cdot 10^{-4}$	$2.01 \cdot 10^{-2}$
Vac _{Cu}	$-1.04 \cdot 10^{-2}$	$1.08 \cdot 10^{-2}$	$5.24 \cdot 10^{-3}$	$-1.85 \cdot 10^{-2}$
Mn _{Cu}	$2.52 \cdot 10^{-3}$	$6.25 \cdot 10^{-4}$	$2.29 \cdot 10^{-3}$	$1.59 \cdot 10^{-3}$
Cu _{Mn}	$6.69 \cdot 10^{-3}$	$-5.32 \cdot 10^{-4}$	$-2.05 \cdot 10^{-3}$	$1.34 \cdot 10^{-2}$
Cu _{As}	$1.70 \cdot 10^{-3}$	$1.03 \cdot 10^{-3}$	$1.66 \cdot 10^{-3}$	$1.80 \cdot 10^{-4}$
As _{Cu}	$2.79 \cdot 10^{-3}$	$1.05 \cdot 10^{-3}$	$2.42 \cdot 10^{-3}$	$1.13 \cdot 10^{-3}$
As _{Mn}	$3.41 \cdot 10^{-3}$	$1.31 \cdot 10^{-3}$	$1.60 \cdot 10^{-3}$	$1.30 \cdot 10^{-3}$
Mn _{As}	$2.95 \cdot 10^{-3}$	$1.20 \cdot 10^{-3}$	$2.47 \cdot 10^{-3}$	$9.98 \cdot 10^{-4}$
Vac _{As}	$2.17 \cdot 10^{-3}$	$1.87 \cdot 10^{-5}$	$2.99 \cdot 10^{-3}$	$2.27 \cdot 10^{-3}$
Cu \leftrightarrow Mn	$2.54 \cdot 10^{-1}$	$2.03 \cdot 10^{-1}$	$2.14 \cdot 10^{-1}$	$1.16 \cdot 10^{-1}$

TABLE III. Theoretical AMR, i.e. $(\rho_{xx} - \rho_{yy})/\rho_{av}$, resulting from the microscopical model and $\rho_{av} = (\rho_{xx} + \rho_{yy})/2$. Calculations assume 5% of the respective impurity and magnetic moments along x .

and only a single magnetic moment direction \vec{m} is considered (all $\vec{m}_{1,2}$, \vec{m} and $\vec{b} = \vec{B}/B$ are unit vectors). Magnetic anisotropy (see Appendix A) is assumed to have a uniaxial form (the axis being a general in-plane direction \hat{a}) and it is represented by field B_a . Minimising the energy given by Eqs. 1 or 2, the direction of $\vec{m}_{1,2}$ (or \vec{m}) can be determined for arbitrary direction and magnitude of \vec{B} . Assuming that the AMR is dominated by non-crystalline terms¹⁸

$$\frac{\Delta\rho_{xx}(\phi)}{\rho_0} = C_I \cos 2\phi \quad (3)$$

the angular sweeps in ψ , $\vec{b} \cdot \hat{x} = \cos \psi$ can be simulated. The SW model provides the connection, via energy minimisation, between ψ (as an input) and ϕ (as an output) which is the angle between current direction and \vec{m} or Néel vector.

As a matter of fact, the SW model for both ferromagnet (FM) and antiferromagnet (AFM), Eqs. 1,2, reduces to *almost* the same form if $\vec{m}_{1,2}$ are assumed to lie in plane so that their direction can be represented by a single angle ϕ :

$$\tilde{E} = 2\alpha \cos 2\phi - \frac{1}{2}\beta^n \sin^n(\phi - \psi), \quad (4)$$

where $n = 1$ for a FM and $n = 2$ for an AFM and ψ represents the direction of the magnetic field. Particular expressions for α and β differ for the FM and AFM flavours of the model but in both cases, $\alpha \propto B_a$ relates to the magnetic anisotropy and $\beta \propto B$ describes the effect of external magnetic field; see Appendix A for detailed explanation. We stress that attempts to model the data with biaxial anisotropy (which would be more natural in a tetragonal system) lead to visibly worse quality of fits.

For practical purposes, the difference between \sin and \sin^2 is unimportant in modelling results: in both cases, the second term in Eq. (4) provides a minimum close

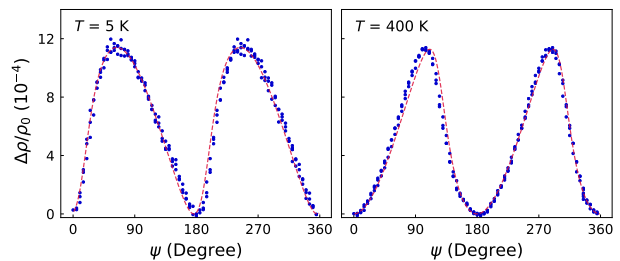


FIG. 6. SW analysis of angular sweeps at maximum B (left/right: low/high temperature). Data taken from Fig. 4.

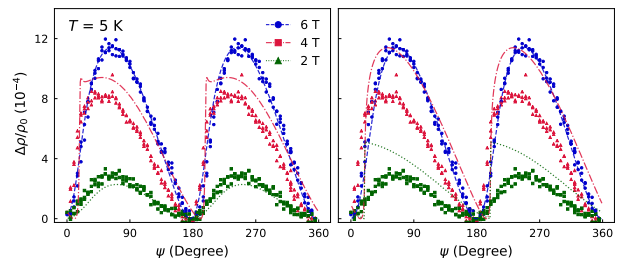


FIG. 7. Analysis of the field-dependence ($T = 5 \text{ K}$ data from Fig. 4) based on two flavors of SW model: (a) AFM, (b) FM.

to $\phi = \psi$. The only substantial difference between the FM and AFM cases is, effectively, how the Zeeman-like term depends on magnetic field ($\propto \beta^2$ for AFM, $\propto \beta$ for FM) and this allows for a straightforward test of experimental data. We first fit the measured data at B large enough for saturation, see Fig. 6, and determine α in Eq. (4) assuming that $\beta = 1$. In Appendix A, we explain the fitting procedure in detail and here we only remark that the effective magnetic anisotropy implied by angular sweeps data does not have the easy axis \vec{a} aligned with any high symmetry direction. Measurements at different temperatures T are consistent with \vec{a} being independent of T whereas the magnitude of the anisotropy $\propto B_a$ does change and even flips the sign. This is manifest in different shapes of data on the left and right panels of Fig. 6.

Next, we use the fitted parameters (B_a from Eq. 1) and look at lower B than the saturation field: the FM model (drop the B_e term in Eq. 1) works much worse than the AFM model in Fig. 7(a). This suggests that it is not free magnetic moments (or ferromagnetic inclusions such as MnAs nanocrystals) that responds to B but rather, an antiferromagnetic system. It could be that antiferromagnetically coupled pairs of free magnetic moments are responsible but given calculated AMR in Tab. III it appears likely that we observe bulk response of an antiferromagnet even if it is probably only a fraction of its volume (while its substantial part may be strongly pinned by, for example, structural defects).

V. CONCLUSION

Transport properties experimentally investigated in this work are the magnetoresistance and temperature-dependent resistivity. As for the latter, we find a reasonable agreement between the large structural anisotropy (at low temperatures, the out-of-plane resistivity is almost seven times larger than the in-plane resistivity) and model calculations which show similar, even if typically somewhat smaller, anisotropy regardless of the impurity type. This anisotropy is therefore likely to arise due to layered structure of tetragonal CuMnAs. We encounter frequent violations of Matthiessen rule: for varied concentrations of static impurities, for different types of chemical disorder (at $T = 0$) and also for phonons and magnons. Anisotropic magnetoresistance (AMR) measured is modest in magnitude and phenomenological modelling indicates the presence of in-plane uniaxial anisotropy which is not oriented along any special crystallographic direction. It is at present impossible to conclude what part of our system responds to the applied magnetic field but it is unlikely that the single-domain picture applies.

ACKNOWLEDGEMENTS

Discussions with T. Jungwirth and J. Zubáč are acknowledged as well as the support from National Grid Infrastructure MetaCentrum CESNET (No. LM2015042), the Ministry of Education, Youth and Sports from the Large Infrastructures for Research, Experimental Development and Innovations project 'IT4Innovations National Supercomputing Center – LM2015070', NanoEnviCz (No. LM2015073), Materials Growth and Measurement Laboratory MGML.EU (No. LM2018096, see: <http://mgml.eu>) all provided under the program 'Projects of Large Research, Development, and Innovations Infrastructures'. I.T., J.K. and D.W. acknowledge financial support by contract Nr. 18-07172S from GAČR and P.H. and E.D.N that by ERDF under the project CZ.02.1.01/0.0/0.0/15_003/0000485.

Appendix A: Magnetic anisotropies and SW model

Apart from magnetocrystalline anisotropy energy (MAE), lower than cubic symmetry systems are affected by dipolar interactions as far as their easy axes are concerned.⁴⁰ Using DFT+U calculations,⁴¹ MAE was estimated at 0.130 meV/f.u. favouring the in-plane directions and the dipole-dipole interactions, evaluated using Eq. (A1) of Ref. 40, further increase the energy penalty for magnetic moments along c -axis by 0.04 meV/f.u.

For \vec{m} , \vec{b} lying in-plane, the first term in Eq. (2) can be rewritten using angles ψ , φ as $-B \cos(\psi - \varphi)$ and the

magnetic anisotropy using

$$2 \cos^2(\phi - \phi_0) - 1 = \cos 2\phi_0 \cos 2\phi + \sin 2\phi_0 \sin 2\phi \quad (\text{A1})$$

where $\vec{a} = (\cos \phi_0, \sin \phi_0)$ is the easy axis direction. This allows to immediately identify $\alpha = B_a/B_0$ and $\beta = B/B_0$ in Eq. 4 in the case of ferromagnets (B_0 is a reference field). For antiferromagnets, the derivation of Eq. 4 with $n = 2$ is more involved. First, the two angles related to $\vec{m}_{1,2}$ are reduced to just one (the one related to canting, i.e. effectively $\vec{m}_1 + \vec{m}_2$ can be expressed analytically and then re-inserted into Eq. 1). Direction of the Néel vector, parametrised by angle ψ , remains as a variable with respect to which the energy should be minimised. Eq. 4 with $n = 2$ follows and $\alpha = B_a/B_e$ whereas $\beta = B/B_e$.

Good fits in Fig. 6 are only possible if we allow for nonzero ϕ_0 and, with respect to the [100] crystallographic direction, we find that \vec{a} is inclined by $\approx 15^\circ$ at low temperatures. Biaxial anisotropy can be modelled by replacing $\cos 2\phi$ with $\cos 4\phi$ in Eq. (A1) but fits give a significantly larger χ^2 (about a factor of five) than for uniaxial anisotropy. The difference in quality of the fits (uniaxial and biaxial, both with ϕ_0 as a free parameter) is also clearly visible.

Appendix B: Detailed transport calculations

Tab. I of the main text summarizes the most important results for zero-temperature resistivity. However, various approaches (within CPA based on TB-LMTO) to calculate resistivity can be chosen: Tab. V gives an overview of both scalar and fully relativistic approaches and the effect of Hubbard U and *spd* vs. *spdf* basis is also presented. (We note that data in Tab. II are calculated using the *spdf* basis.) The discrepancies among the values in the table should be considered as an uncertainty of our approach; we note, that a larger basis in the TB-LMTO does not necessary lead to more precise calculations. Resistivities in both Tab. I and V are shown for 5% of the respective impurity and formation energies are taken from Ref. 24. In general, the lowest resistivities are obtained for the scalar relativistic approach and the values are also larger for the *spdf* basis; however, there is no strict trend and various impurities behave differently.

We proceed with a remark on additivity of scattering rates in the context of zero-temperature resistivity. Not only that the Matthiessen rule does not hold for *different* sources of scattering; even with a single type of impurity, doubling its concentration does not necessarily lead to doubling the resistivity. A clear example of this is shown in Fig. 8. The most striking case is that of non-monotonic ρ_{zz} with maxima at 7% and 11% of Vac_{Mn} and Vac_{Cu}, respectively. In the context of binary alloys, these concentrations are relatively low but similar values have been reported for nonmagnetic Pd-Co⁴² and magnetic Ni-Fe and Ni-Co.²⁵ We note, that since these ran-

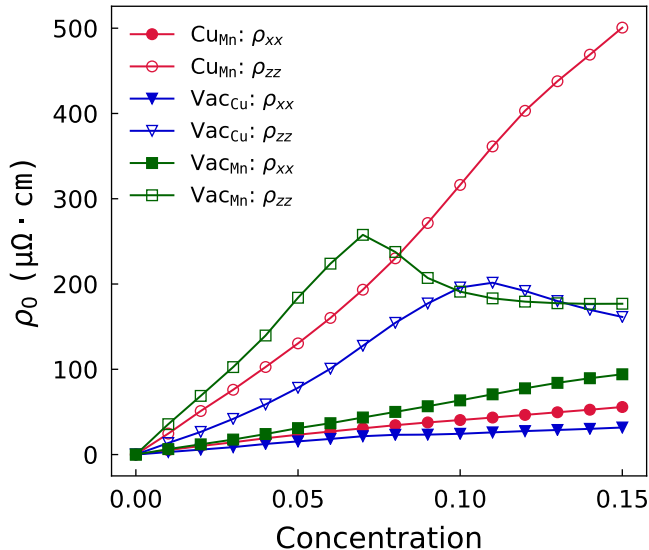


FIG. 8. Zero-temperature resistivity for three different types of impurities as a function of concentration of the respective impurity.

dom alloys are cubic, the anisotropy is of minor influence there.

Non-monotonic dependence of ρ_{zz} on impurity concentration occurs also for the more complex model mentioned in Fig. 2. As a consequence, increasing the concentration of $\text{Cu}_{\text{Mn}}^{\text{vac}}$ does not improve the agreement with experimental data, see Fig. 9. Temperature-dependence of resistance, nevertheless, agrees reasonably well as far as phonons are concerned and this applies to a larger group of impurities. Linear function was fitted to $\rho_{xx}(T)$ and $\rho_{zz}(T)$ in the range from 0 K to 180 K and the linear coefficients⁴³ are shown in Tab. IV. Negative values of these coefficients are usually not observed in experiments; nevertheless, measured resistance may decrease with growing chemical disorder and this is also seen in our model results of Fig. 8. Obtained linear coefficients for $\rho_{zz}(T)$ (shown in Tab. IV) are much more sensitive to the kind of the impurity than in the case of $\rho_{xx}(T)$, i.e., the standard deviation of the average value (of the calculated data) is more than 110 % for $\rho_{zz}(T)$ while similar analysis for $\rho_{xx}(T)$ gives standard deviation below 30 %. Together with formation energies and residual resistivities (Tab. I and V), the trends may be used to determine the most probable defects.

To give another example of phononic effects, we show temperature-dependent resistivity for vac_{Cu} and vac_{Mn} in Fig. 10. Note that the linear coefficients of $\rho_{zz}(T)$ in Tab. IV are in a very good agreement with experimental values for these impurities. Combining Fig. 10 with Fig. 5 leads to different resistivities than what is shown in Fig. 9 thus demonstrating the failure of the Matthiessen rule once again.

We conclude this appendix by several comments on the correlation of resistivity to the density of states (DOS)

Defect	ρ_{xx} [$\mu\Omega$ cm K^{-1}]	ρ_{zz} [$\mu\Omega$ cm K^{-1}]
As_{Mn}	0.32 ± 0.03	-0.76 ± 0.06
As_{Cu}	0.40 ± 0.02	-0.43 ± 0.14
Mn_{As}	0.37 ± 0.03	-0.20 ± 0.03
Cu_{As}	0.35 ± 0.05	0.29 ± 0.11
$\text{Cu} \leftrightarrow \text{Mn}$	0.45 ± 0.05	0.43 ± 0.10
Vac_{As}	0.34 ± 0.02	0.52 ± 0.17
Mn_{Cu}	0.44 ± 0.05	0.68 ± 0.01
$\text{Cu}_{\text{Mn}} : 10\%$	0.47 ± 0.04	1.29 ± 0.07
Vac_{Cu}	0.48 ± 0.09	1.30 ± 0.19
Vac_{Mn}	0.46 ± 0.07	1.33 ± 0.07
$\text{Cu}_{\text{Mn}} : 5\%$	0.54 ± 0.05	1.51 ± 0.09
$\text{Cu}_{\text{Mn}} : 2\%$	0.62 ± 0.09	1.59 ± 0.18
No impurity	0.70 ± 0.23	1.62 ± 0.41
Experiment	0.23 ± 0.01	1.30 ± 0.02

TABLE IV. Linear coefficient from $\rho(T)$ fits up to $T = 180$ K, uncertainties were obtained from the fit, and calculated data (*spdf*, $U = 0.00$ Ry) are sorted by the last column. The last row shows the same coefficients from the measured values.

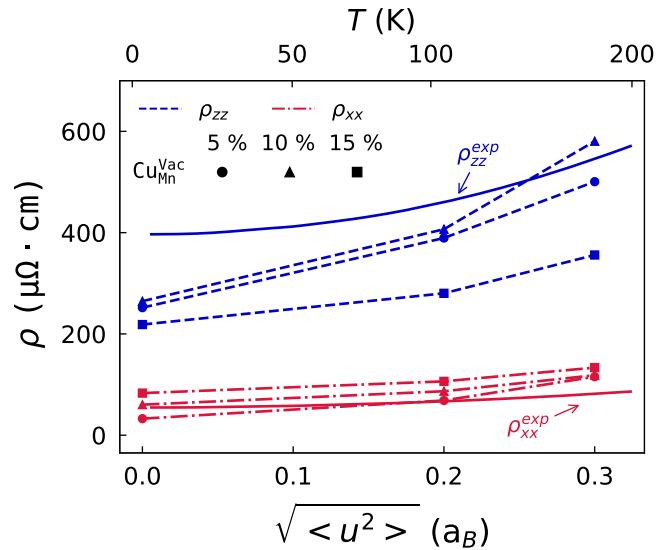


FIG. 9. Model calculations of $\rho(T)$, sources of scattering¹⁷ are $\text{Cu}_{\text{Mn}}^{\text{vac}}$ and phonons.

at the Fermi level E_F . The saturation of $\rho_{xx}(T)$ and the decrease of $\rho_{zz}(T)$ (with increasing temperature) caused by magnons was attributed in Ref. 22 to a high increase of DOS at the Fermi level. Here we observe decreasing $\rho_{zz}(T)$ due to phonons for some impurities but $\rho_{xx}(T)$ having reasonable metallic-like increase. It is shown in Tab. IV (negative slopes) and in Fig. 5 and we also tried to address it on the level of the DOS. (The energy dependent DOS were calculated, but they are not shown here for brevity; they are presented in Refs. 22 and 24). For clean stoichiometric CuMnAs , the DOS is strongly increasing above E_F , i.e., there are about twenty states

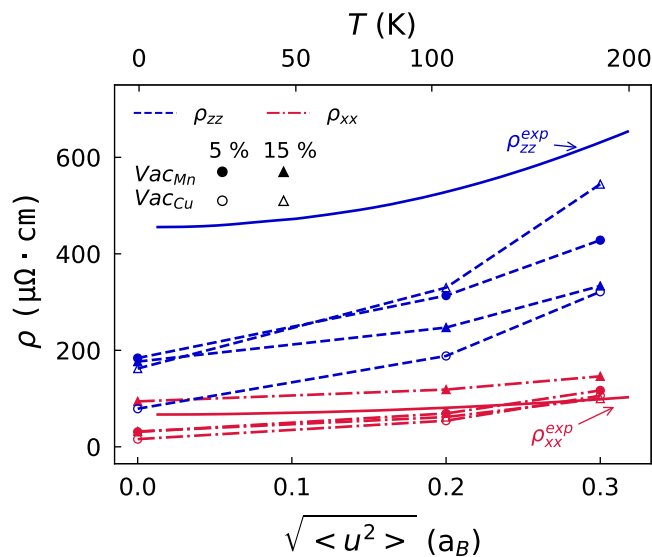


FIG. 10. Model calculations analogous to Fig. 9 with vacancies on Cu and Mn sites instead of $\text{Cu}_{\text{Mn}}^{\text{vac}}$.

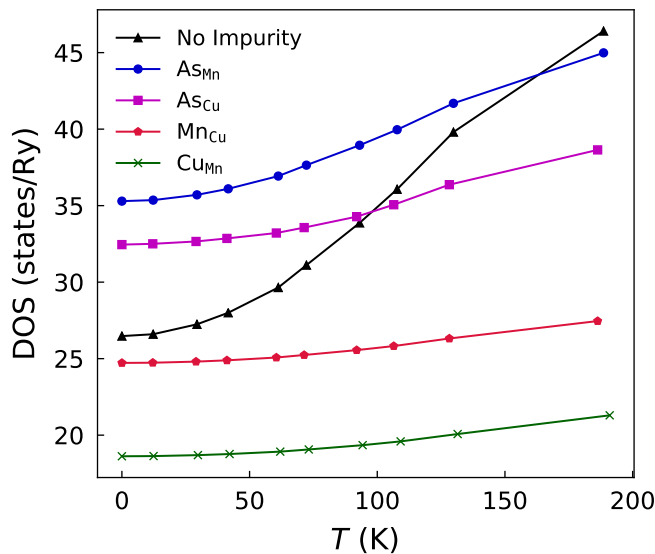


FIG. 11. Total DOS at E_F with only phononic contribution to temperature. CuMnAs with no impurities is shown by black line with crosses and 5 % of AS_{Mn} , AS_{Cu} , Mn_{Cu} , and Cu_{Mn} is depicted by gray circles, blue triangles, green squares, and red diamonds, respectively.

per Ry at E_F , while four times more for $E > E_F + 0.2$ eV. Under the presence of phonons, this region of high DOS is smeared (more precisely: large self-energy leads to a large broadening of the spectral function) and for the stoichiometric CuMnAs, situation at E_F is appreciably modified for $T \gtrsim 100$ K (see the black line with crosses in Fig. 11). The drop of $\rho_{zz}(T)$ in Fig. 5 begins around 200 K which can be expected given the fact that the increase of DOS with temperature is initially compensated by an increase of self-energy. We note that no similar decrease with temperature is observed for $\rho_{xx}(T)$; this could be caused by the layered structure of CuMnAs, but directionally resolved study of the states, e.g., in the terms of the Bloch spectral function similarly to previously investigated NiMnSb³⁶, is beyond the scope of this paper. Although we attribute the phonon-induced decrease of resistivity to the DOS specific for CuMnAs, it could occur also for other metals having similar DOS.

¹ V. Baltz, A. Manchon, T. Moriyama, T. Ono, and Y. Tserkovnyak, Rev. Mod. Phys. 90, 015005 (2018); T. Jungwirth et al., Nat. Phys. 14, 200 (2018).
² Z. Kašpar et al., arxiv 1909.09071
³ P. Wadley et al., Nat. Nanotechn. 13, 362 (2018).
⁴ M. Veis et al., Phys. Rev. B 97, 125109 (2018).
⁵ J. Železný et al., Phys. Rev. Lett. 113, 157201 (2014).

⁶ P. Wadley et al., Science 351, 587 (2016).
⁷ K. Olejník et al., Nat. Comm. (2017). doi: 10.1038/ncomms15434
⁸ P. Wadley et al., Nat. Comm. (2013). doi: 10.1038/ncomms3322
⁹ Sect. B-A J. Chem. Sci 47, 925 (1992)
¹⁰ F. Krizek et al., arxiv 1911.01794

- ¹¹ K. Uhlřřova et al., J. All. Compd. 650, 224 (2015).
- ¹² E. Emmanouilidou et al., Phys. Rev. B 96, 224405 (2017).
- ¹³ K. Uhlřřova et al., J. Alloys Compd. 771, 680 (2019).
- ¹⁴ P.J.W. Moll et al., Nat. Commun. 6, 6663 (2015).
- ¹⁵ P.J.W. Moll et al., Science 351, 1061 (2016).
- ¹⁶ P.J.W. Moll et al., Nature 535, 266 (2016).
- ¹⁷ $\text{Cu}_{\text{Mn}}^{\text{vac}}$ denotes a 'combined' impurity where a Cu atom is removed from its original position and put at Mn site, i.e. effectively a combination of Cu_{Mn} and vac_{Cu} single-atomic impurities.
- ¹⁸ A.W. Rushforth et al., Phys. Rev. Lett. 99, 147207 (2007).
- ¹⁹ To be precise, we measured ρ_{xx} for different directions of \vec{B} rather than ρ_{xx} different from ρ_{yy} for the same \vec{B} . Given the tetragonal symmetry, however, the two cases are directly related.
- ²⁰ I. Turek, V. Drchal, J. Kudrnovsky, M. Šob, and P. Weinberger: Electronic Structure of Disordered Alloys, Surfaces and Interfaces, 1st ed. (Kluwer Academic Publishers, 1997)
- ²¹ S.H. Vosko et al., Can. J. Phys. 58, 1200 (1980).
- ²² D. Wagenknecht et al., arxiv 1912.08025 (2019).
- ²³ F. Maca et al., Phys. Rev. B 96, 094406 (2017).
- ²⁴ F. Maca et al., J. Magn. Magn. Mat. 474, 467 (2019).
- ²⁵ I. Turek et al., Phys. Rev. B 86, 014405 (2012).
- ²⁶ I. Turek et al., Phys. Rev. B 65, 125101 (2002).
- ²⁷ K. Carva et al., Phys. Rev. B 73, 144421 (2006).
- ²⁸ I. Turek et al., Phys. Rev. B 89, 064405 (2014).
- ²⁹ H. Ebert et al., Phys. Rev. B 91, 165132 (2015).
- ³⁰ D. Kodderitzsch et al., New J. Phys. 15, 053009 (2013).
- ³¹ J.K. Glasbrenner, B.S. Pujari and K.D. Belashchenko, Phys. Rev. B 89, 174408 (2014).
- ³² A.A. Starikov et al., Phys. Rev. B 97, 214415 (2018).
- ³³ D. Wagenknecht, K. Carva and I. Turek, IEEE Transactions on Magnetics 53, 1700205 (2017).
- ³⁴ D. Wagenknecht, K. Carva and I. Turek, Proceedings SPIE (2017), doi: 10.1117/12.2273315.
- ³⁵ D. Wagenknecht et al., J. Magn. Magn. Mat. 474, 517 (2019).
- ³⁶ D. Wagenknecht et al., Phys. Rev. B 99, 174433 (2019).
- ³⁷ Anton A. Starikov, Yi Liu, Zhe Yuan, and Paul J. Kelly, Phys. Rev. B 97, 214415
- ³⁸ J.B. Staunton et al., Phys. Rev. Lett. 93, 257204 (2004); J.B. Staunton et al., Phys. Rev. B 74, 144411 (2006).
- ³⁹ E.C.Stoner and E.P. Wohlfarth, Phil. Trans. Roy. Soc. A 240 (1948). doi: 10.1098/rsta.1948.0007
- ⁴⁰ C.A.Correa and K. Vyborny, Phys. Rev. B 97, 235111 (2018).
- ⁴¹ P. Wadley et al., Sci. Rep. 5, 17079 (2015).
- ⁴² J. Kudrnovsky et al., Phys. Rev. B 92, 224421 (2015).
- ⁴³ Because of finite-temperature scattering mechanism, it would be more appropriate to use a quadratic function⁴⁴, but we do not have enough data for all of the impurities to perform this analysis reliably and the linear function is sufficient to present trends implied by phonons.
- ⁴⁴ V. Drchal et al., PRB 98, 134442 (2018).

Defect	Formation energy ²⁴ [eV]	Scalar rel., <i>spd</i>		Fully rel., <i>spd</i>				Fully rel., <i>spdf</i>			
		$U = 0.00$ Ry		$U = 0.00$ Ry		$U = 0.10$ Ry		$U = 0.00$ Ry		$U = 0.10$ Ry	
		ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}	ρ_{xx}	ρ_{zz}
Vac _{Mn}	-0.16	36	155	32	154	19	134	31	184	20	181
Vac _{Cu}	-0.14	12	44	12	54	9	57	16	79	11	92
Mn _{Cu}	-0.03	111	171	115	203	132	683	112	263	150	915
Cu _{Mn}	0.34	24	122	22	130	8	40	23	131	8	57
Cu _{As}	1.15	107	273	109	377	144	989	121	481	163	1299
As _{Cu}	1.73	94	219	98	257	112	530	114	359	123	694
As _{Mn}	1.79	113	262	124	240	133	455	141	476	161	617
Mn _{As}	1.92	122	151	130	270	155	854	147	423	186	1784
Vac _{As}	2.18	174	203	182	246	219	1054	210	306	284	1556
Cu \leftrightarrow Mn	-	124	267	123	304	127	629	120	393	142	882

TABLE V. Detailed microscopic calculations of resistivities in $\mu\Omega\cdot\text{cm}$ for 5% of the respective impurity.